中国认可
国际互认
检测
TESTING
CNAS L6069

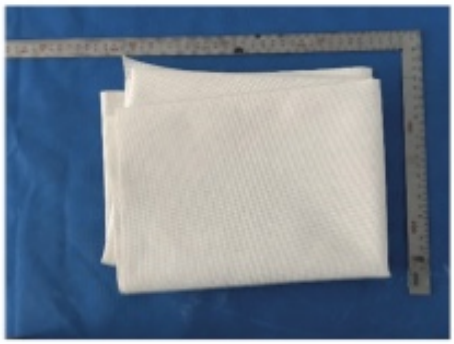
Report No. TC.19.04.002205

Date of Issue 04/26/2019

Applicant: JALPERSAN PERDE SİSTEMLERİ TEKSTİL VE MOB. AKS. İNŞ. SAN. VE TİC. LTD. ŞTİ.

Applicant address: ASO 2. VE 3.OSB ESKİŞEHİR YOLU 42. KM, 2021 CADDE NO:8, 06930 ALCI OSB/SİNCAN/ANKARA

Description of the test subject:

Sample	Description	Photo
001	Sample Description: Sunshine fabric Style No.: 1080-1 Structure: PVC coated polyester fabric Material: 70% PVC+30% Polyester Color: White Thickness: 0.55mm End use: Sunshine fabric	

Receipt Date of Sample: 04/18/2019

Date of Testing: From 04/18/2019 to 04/26/2019

Sample submitted: The sample(s) was (were) submitted by applicant and identified.

Conclusion:

Test Items			Result
No.	Items	Standard	
1	Methods of Fire Tests For Flame Propagation of Textiles and Films	NFPA 701:2015 Method 1	Pass

Note: (1) General Terms & Conditions as mentioned overleaf,(2)The results relate only to the items tested,(3)The test report shall not be reproduced except in full without the written approval of the company. (4) Samples are tested as received.

Changzhou Jintan Railway Transportation Technical Service Co.,Ltd.
Phone: +86/ (0) 519-8123-9872
Fax: +86/ (0) 519-8123-9872 ext.123
E-mail: hui.shen@tuv-sud.cn
www.tuv-sud.cn
No. 164, Wuyi Road ,Lucheng Street, Wujin District, Changzhou city, Jiangsu Province, 213015 P.R. China

中国认可
国际互认
检测
TESTING
CNAS L6069

Report No. TC.19.04.002205

Date of Issue 04/26/2019

Test Results

Test method 1 of NFPA 701:2015 Standard Methods of Fire Tests for Flame Propagation of Textiles and Films

1. Conditioning

Prior to testing	at least 30 minutes at 105℃ ±3℃
Size of sample	150mm × 400mm 10pcs 419 g/m²

2. Test results

Specimen No:	Mass of specimen Before test (g)	Mass of specimen After test (g)	Mass loss (Percent)	After flame time (s)	Burning time on floor (s)
1	26.35	23.84	9.53	0	--
2	27.41	24.43	10.87	0	--
3	26.89	23.31	13.31	0	--
4	27.21	23.99	11.83	0	--
5	26.46	24.01	9.26	0	--
6	27.02	23.87	11.66	0	--
7	26.29	23.46	10.76	0	--
8	27.36	24.27	11.29	0	--
9	26.69	23.30	12.70	0	--
10	27.49	24.39	11.28	0	--
AVE	--	--	11.25	0	--

Criteria for test method 1 (Chapter 10):

1. Fragments or residues of specimens that fall to the floor of the test chamber shall not continue to burn for more than an average of 2 seconds per specimen for the sample of 10 specimen.
2. The average weight loss of the 10 specimen in a sample shall be 40 percent or less.
3. No individual specimen's percent mass loss shall deviate more than 3 standard deviations from the mean for the 10 specimens.

Note: (1) General Terms & Conditions as mentioned overleaf,(2)The results relate only to the items tested,(3)The test report shall not be reproduced except in full without the written approval of the company. (4) Samples are tested as received.

Changzhou Jinbao Railway Transportation Technical Service Co.,Ltd.

Phone: +86/ (0) 519-8123-9872
Fax: +86/ (0) 519-8123-9872 ext.123
E-mail: hui.shen@tuv-sud.cn
www.tuv-sud.cn

No. 164, Wuyi Road ,Lucheng Street, Wujin District, Changzhou city, Jiangsu Province, 213015 P.R. China

Report No. **TC.19.04.002205**

Date of Issue **04/26/2019**

4. When a retest is required, no individual specimen's percent mass loss in the second set of specimens shall deviate from the mean value by more than 3 standard deviations calculated for the second set.
5. When a sample does not demonstrate passing performance in accordance with all of the conditions indicated above, the material shall be recorded as having failed Test Method 1.

3. Observations:

Vigorousness of burning	No
Material molten dripping	No

Conclusion: The tested sample "As received" **meets** the requirements of Test Method 1 of NFPA 701:2015.

Statement: The test results relate to the behaviour of the test specimens of a product under the particular conditions of the test; they are not intended to the sole criterion for assessing the potential smoke and toxicity hazard of the product in use.

Changzhou Jinbiao Railway Transportation Technical Service Co., Ltd.

Drafted by: Approved by:

Lynn liu Shen hui

-End of Report-

Note: (1) General Terms & Conditions as mentioned overleaf,(2)The results relate only to the items tested,(3)The test report shall not be reproduced except in full without the written approval of the company. (4) Samples are tested as received.

Changzhou Jinbiao Railway Transportation Technical Service Co.,Ltd.
Phone: +86/ (0) 519-8123-9872
Fax: +86/ (0) 519-8123-9872 ext.123
E-mail: hui.shen@tuv-sud.cn
www.tuv-sud.cn
No. 164, Wuyi Road ,Lucheng Street, Wujin District, Changzhou city, Jiangsu Province, 213015 P.R. China